

試驗報告



報告編號： TB-21-02219
C-21-05789

頁數： 1 OF 1

報告日期： 110年05月19日

工程名稱：自測
 承包商：-----
 委託單位：薪豐豐業有限公司/麒豐豐業有限公司
 供料廠商：-----
 樣品名稱：F1防潮粒片板
 取樣人員：薪豐豐業有限公司
 送驗人員：薪豐豐業有限公司
 收件日期：110年04月22日
 試驗日期：110年04月22日~110年05月19日
 備註：1.以上資料由顧客提供(收件及試驗日期除外)
 2.除非另有說明，此報告結果僅對測試之樣品負責
 未經本公司事先書面同意，此報告不可部分複製
 3.下述報告內容標示#處由顧客提供

本報告內容標示#處由顧客提供

=====
 試驗結果：

試驗項目	試驗結果	試驗方法
吸水厚度膨脹率 (%)	3	CNS 2215(2012)
抗彎強度 (N/mm ²)	13.1	
耐衝擊性 (W ₂ -500, 100 cm)	無龜裂、破壞及剝離的情形 (平均凹陷直徑 13 mm)	
木螺釘保持力 (N)	441	
內聚強度 (N/mm ²)	0.7	

註：1.試驗樣品厚度為 18.2 mm
 2.本試驗報告抗彎強度及耐衝擊性試驗為TAF認證範圍，其餘則非
 3.本試驗報告之試驗地點同實驗室地址

----- oOo -----

耐

報告簽署人

本報告若有提供規範值時，該規範值僅供參考，合格之判定以委託單位實際要求為準

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com.tw/Terms-and-Conditions> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com.tw/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.

試驗報告




報告編號：TB-21-02220
C-21-05790

頁數：1 OF 1

報告日期：110年05月19日

工程名稱：自測
 承包商：----
 委託單位：薪豐豐業有限公司/麒豐豐業有限公司
 供料廠商：----
 樣品名稱：F1防潮粒片板
 取樣人員：薪豐豐業有限公司
 送驗人員：薪豐豐業有限公司
 收件日期：110年04月22日
 試驗日期：110年04月22日~110年05月12日
 備註：1.以上資料由顧客提供(收件及試驗日期除外)
 2.除非另有說明，此報告結果僅對送試之樣品負責
 未經本公司事先書面同意，此報告不可部分複製
 3.下述報告內容標示#處由顧客提供

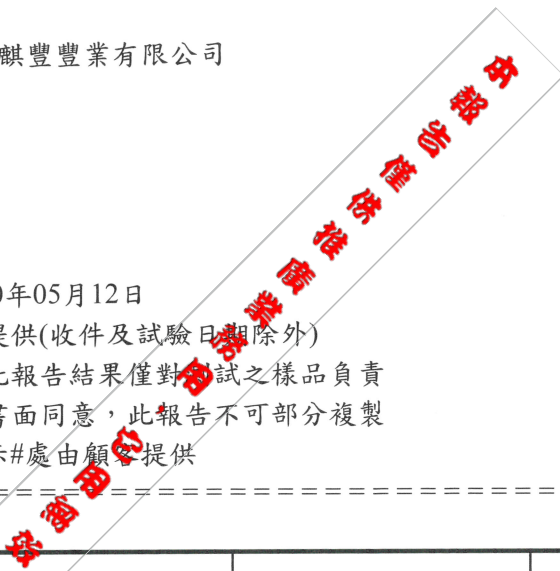


試驗結果：

試驗項目	試驗結果	方法偵測極限(MDL)	試驗方法
甲醛釋出量-最大值 (mg/L)	0.3	0.05	CNS 2215(2012)
甲醛釋出量-平均值 (mg/L)	0.3	0.05	

- 註： 1.試驗樣品厚度為 18.1 mm
 2.試驗結果若低於方法偵測極限值(MDL)之測定值以"N.D."表示；
 若高於方法偵測極限值(MDL)，但低於定量極限值(QDL)時，以"< 0.2"表示，
 並括號註明其實測值
 3.N.D. = Not Detected / 未檢出
 # 4.CNS 2215(2012)規定甲醛釋出量 F₁規範值為最大值 0.4 mg/L以下，平均值 0.3 mg/L以下
 F₂規範值為最大值 0.7 mg/L以下，平均值 0.5 mg/L以下
 F₃規範值為最大值 2.1 mg/L以下，平均值 1.5 mg/L以下
 5.本試驗報告之試驗地點同實驗室地址

----- oOo -----

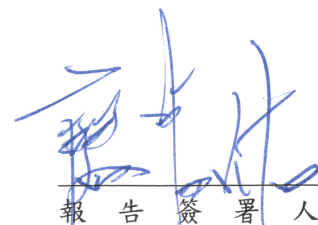

報告簽署人

本報告若有提供規範值時，該規範值僅供參考，合格之判定以委託單位實際要求為準

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com.tw/Terms-and-Conditions> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com.tw/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.

試驗報告



報告編號：TB-21-02221

C-21-05791

頁數：1 OF 1

報告日期：110年05月21日

工程名稱：自測
 承包商：----
 委託單位：薪豐豐業有限公司/麒豐豐業有限公司
 供料廠商：----
 樣品名稱：F1防潮粒片板
 取樣人員：薪豐豐業有限公司
 送驗人員：薪豐豐業有限公司
 收件日期：110年04月22日
 試驗日期：110年04月22日~110年05月19日

- 備註：1.以上資料由顧客提供(收件及試驗日期除外)
 2.除非另有說明，此報告結果僅對測試之樣品負責
 未經本公司事先書面同意，此報告不得部分複製
 3.下述報告內容標示#處由顧客提供

試驗結果：

試驗項目	試驗結果			# CNS 11668(2008) 規範要求值	試驗方法
	測定項目	SAMPLE 1	SAMPLE 2		
防焰性	火源加熱時間(min)	2	2	2	CNS 11668(2008)
	餘焰時間(sec)	1	3	10 sec 以下	
	餘燼時間(sec)	1	3	30 sec 以下	
	炭化面積(cm ²)	23	22	50 cm ² 以下	

註：1.試驗樣品厚度：SAMPLE 1為18.1 mm；SAMPLE 2為18.2 mm

2.測試面為正面

3.本試驗之樣品不在TAF認證範圍內，故無法出具TAF標誌之報告

4.本試驗報告之試驗地點同實驗室地址

----- oOo -----

本報告若有提供規範值時，該規範值僅供參考，合格之判定以委託單位實際要求為準

報告簽署人

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com.tw/Terms-and-Conditions> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com.tw/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.

試驗報告



報告編號：TB-21-02222

C-21-05792

頁數：1 OF 1

報告日期：110年05月12日

工程名稱：自測
 承包商：-----
 委託單位：薪豐豐業有限公司/麒豐豐業有限公司
 供料廠商：-----
 樣品名稱：F1防潮粒片板
 取樣人員：薪豐豐業有限公司
 送驗人員：薪豐豐業有限公司
 收件日期：110年04月22日
 試驗日期：110年04月22日~110年05月12日
 備註：1.以上資料由顧客提供(收件及試驗日期除外)
 2.除非另有說明，此報告結果僅對測試之樣品負責
 未經本公司事先書面同意，此報告不可部分複製
 3.下述報告內容標示#處由顧客提供


本報告僅供參考，請認明SGS商標

試驗結果：

試驗項目	試驗結果	試驗方法
耐酸性 (5%乙酸水溶液)	不變色	CNS 2215(2012)
耐鹼性 (1%碳酸鈉水溶液)	不變色	
紅色蠟筆之耐污染性	污染用灰色標 4-5 號	

註：本試驗報告之試驗地點同實驗室地址

----- oOo -----


 報告簽署人

本報告若有提供規範值時，該規範值僅供參考，合格之判定以委託單位實際要求為準

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com.tw/Terms-and-Conditions> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com.tw/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.

試驗報告



報告編號：TB-21-02223

C-21-05793

頁數：1 OF 1

報告日期：110年05月13日

工程名稱：自測
承包商：-----
委託單位：薪豐豐業有限公司/麒豐豐業有限公司
供料廠商：-----
樣品名稱：F1防潮粒片板
取樣人員：薪豐豐業有限公司
送驗人員：薪豐豐業有限公司
收件日期：110年04月22日
試驗日期：110年04月22日~110年05月13日
備註：1.以上資料由顧客提供(收件及試驗日期除外)
2.除非另有說明，此報告結果僅對測試之樣品負責
未經本公司事先書面同意，此報告不可部分複製
3.下述報告內容標示#處由顧客提供

SGS 謹此聲明
本報告內容
未經本公司
事先書面同意
不可部分複製

試驗結果：

試驗項目	試驗結果	試驗方法
濕潤抗彎強度-A試驗 (N/mm ²)	6.6	CNS 2215(2012)

註：1.試驗樣品厚度為 18.1 mm
2.本試驗報告之試驗地點同實驗室地址

----- oOo -----

報告簽署人

本報告若有提供規範值時，該規範值僅供參考，合格之判定以委託單位實際要求為準

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com.tw/Terms-and-Conditions> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com.tw/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.